

ISSN 2518-1491 (Online),  
ISSN 2224-5286 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ  
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ

Д.В.Сокольский атындағы «Жанармай,  
катализ және электрохимия институты» АҚ

# Х А Б А Р Л А Р Ы

---

---

## ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК  
РЕСПУБЛИКИ КАЗАХСТАН  
АО «Институт топлива, катализа и  
электрохимии им. Д.В. Сокольского»

## NEWS

OF THE ACADEMY OF SCIENCES  
OF THE REPUBLIC OF KAZAKHSTAN  
JSC «D.V. Sokolsky institute of fuel, catalysis  
and electrochemistry»

**SERIES**  
**CHEMISTRY AND TECHNOLOGY**

**3 (435)**

**MAY - JUNE 2019**

PUBLISHED SINCE JANUARY 1947

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

---

*NAS RK is pleased to announce that News of NAS RK. Series of chemistry and technologies scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of chemistry and technologies in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of chemical sciences to our community.*

*Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Химия және технология сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Химия және технология сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді химиялық ғылымдар бойынша контентке адалдығымызды білдіреді.*

*НАН РК сообщает, что научный журнал «Известия НАН РК. Серия химии и технологий» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по химическим наукам для нашего сообщества.*

Б а с р е д а к т о р ы  
х.ғ.д., проф., ҚР ҰҒА академигі **М.Ж. Жұрынов**

Р е д а к ц и я а л қ а с ы:

**Ағабеков В.Е.** проф., академик (Белорус)  
**Волков С.В.** проф., академик (Украина)  
**Воротынцев М.А.** проф., академик (Ресей)  
**Газалиев А.М.** проф., академик (Қазақстан)  
**Ергожин Е.Е.** проф., академик (Қазақстан)  
**Жармағамбетова А.К.** проф. (Қазақстан), бас ред. орынбасары  
**Жоробекова Ш.Ж.** проф., академик (Қырғыстан)  
**Иткулова Ш.С.** проф. (Қазақстан)  
**Манташян А.А.** проф., академик (Армения)  
**Пралиев К.Д.** проф., академик (Қазақстан)  
**Баешов А.Б.** проф., академик (Қазақстан)  
**Бүркітбаев М.М.** проф., академик (Қазақстан)  
**Джусипбеков У.Ж.** проф. корр.-мүшесі (Қазақстан)  
**Молдахметов М.З.** проф., академик (Қазақстан)  
**Мансуров З.А.** проф. (Қазақстан)  
**Наурызбаев М.К.** проф. (Қазақстан)  
**Рудик В.** проф., академик (Молдова)  
**Рахимов К.Д.** проф. академик (Қазақстан)  
**Стрельцов Е.** проф. (Белорус)  
**Тәшімов Л.Т.** проф., академик (Қазақстан)  
**Тодераш И.** проф., академик (Молдова)  
**Халиков Д.Х.** проф., академик (Тәжікстан)  
**Фарзалиев В.** проф., академик (Әзірбайжан)

«ҚР ҰҒА Хабарлары. Химия және технология сериясы».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» Республикалық қоғамдық бірлестігі (Алматы қ.)

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде 30.04.2010 ж. берілген №1089-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,  
<http://chemistry-technology.kz/index.php/en/arhiv>

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2019

Типографияның мекенжайы: «Аруна» ЖК, Алматы қ., Муратбаева көш., 75.

Главный редактор  
д.х.н., проф., академик НАН РК **М. Ж. Журинов**

Редакционная коллегия:

**Агабеков В.Е.** проф., академик (Беларусь)  
**Волков С.В.** проф., академик (Украина)  
**Воротынцев М.А.** проф., академик (Россия)  
**Газалиев А.М.** проф., академик (Казахстан)  
**Ергожин Е.Е.** проф., академик (Казахстан)  
**Жармагамбетова А.К.** проф. (Казахстан), зам. гл. ред.  
**Жоробекова Ш.Ж.** проф., академик (Кыргызстан)  
**Иткулова Ш.С.** проф. (Казахстан)  
**Манташян А.А.** проф., академик (Армения)  
**Пралиев К.Д.** проф., академик (Казахстан)  
**Баешов А.Б.** проф., академик (Казахстан)  
**Буркитбаев М.М.** проф., академик (Казахстан)  
**Джусипбеков У.Ж.** проф. чл.-корр. (Казахстан)  
**Мулдахметов М.З.** проф., академик (Казахстан)  
**Мансуров З.А.** проф. (Казахстан)  
**Наурызбаев М.К.** проф. (Казахстан)  
**Рудик В.** проф., академик (Молдова)  
**Рахимов К.Д.** проф. академик (Казахстан)  
**Стрельцов Е.** проф. (Беларусь)  
**Ташимов Л.Т.** проф., академик (Казахстан)  
**Тодераш И.** проф., академик (Молдова)  
**Халиков Д.Х.** проф., академик (Таджикистан)  
**Фарзалиев В.** проф., академик (Азербайджан)

«Известия НАН РК. Серия химии и технологии».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан» (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10893-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел. 272-13-19, 272-13-18,  
<http://chemistry-technology.kz/index.php/en/arhiv>

---

© Национальная академия наук Республики Казахстан, 2019

Адрес редакции: 050100, г. Алматы, ул. Кунаева, 142,  
Институт органического катализа и электрохимии им. Д. В. Сокольского,  
каб. 310, тел. 291-62-80, факс 291-57-22, e-mail:orgcat@nursat.kz

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75

## E d i t o r i n c h i e f

doctor of chemistry, professor, academician of NAS RK **M.Zh. Zhurinov**

## E d i t o r i a l b o a r d :

**Agabekov V.Ye.** prof., academician (Belarus)  
**Volkov S.V.** prof., academician (Ukraine)  
**Vorotyntsev M.A.** prof., academician (Russia)  
**Gazaliyev A.M.** prof., academician (Kazakhstan)  
**Yergozhin Ye.Ye.** prof., academician (Kazakhstan)  
**Zharmagambetova A.K.** prof. (Kazakhstan), deputy editor in chief  
**Zhorobekova Sh.Zh.** prof., academician ( Kyrgyzstan)  
**Itkulova Sh.S.** prof. (Kazakhstan)  
**Mantashyan A.A.** prof., academician (Armenia)  
**Praliyev K.D.** prof., academician (Kazakhstan)  
**Bayeshov A.B.** prof., academician (Kazakhstan)  
**Burkitbayev M.M.** prof., academician (Kazakhstan)  
**Dzhusipbekov U.Zh.** prof., corr. member (Kazakhstan)  
**Muldakhmetov M.Z.** prof., academician (Kazakhstan)  
**Mansurov Z.A.** prof. (Kazakhstan)  
**Nauryzbayev M.K.** prof. (Kazakhstan)  
**Rudik V.** prof., academician (Moldova)  
**Rakhimov K.D.** prof., academician (Kazakhstan)  
**Streltsov Ye.** prof. (Belarus)  
**Tashimov L.T.** prof., academician (Kazakhstan)  
**Toderash I.** prof., academician (Moldova)  
**Khalikov D.Kh.** prof., academician (Tadjikistan)  
**Farzaliyev V.** prof., academician (Azerbaijan)

**News of the National Academy of Sciences of the Republic of Kazakhstan. Series of chemistry and technology.**  
**ISSN 2518-1491 (Online),**  
**ISSN 2224-5286 (Print)**

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty)

The certificate of registration of a periodic printed publication in the Committee of Information and Archives of the Ministry of Culture and Information of the Republic of Kazakhstan N 10893-Ж, issued 30.04.2010

Periodicity: 6 times a year

Circulation: 300 copies

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,

<http://chemistry-technology.kz/index.php/en/arhiv>

---

© National Academy of Sciences of the Republic of Kazakhstan, 2019

Editorial address: Institute of Organic Catalysis and Electrochemistry named after D. V. Sokolsky  
142, Kunayev str., of. 310, Almaty, 050100, tel. 291-62-80, fax 291-57-22,  
e-mail: orgcat@nursat.kz

Address of printing house: ST "Aruna", 75, Muratbayev str, Almaty

**NEWS**

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

**SERIES CHEMISTRY AND TECHNOLOGY**

ISSN 2224-5286

<https://doi.org/10.32014/2019.2518-1491.33>

Volume 3, Number 435 (2019), 77 – 83

UDK 541.135.7:669.35'5

SRSTI 31.15.33

**R.N. Nurdillayeva<sup>1</sup>, A.B. Bayeshov<sup>2</sup>, L.A. Sunatullayeva<sup>1</sup>, G.N. Zhylysbayeva<sup>1</sup>**<sup>1</sup>Khoja Akhmet Yassawi International Kazakh-Turkish University, Turkistan<sup>2</sup>D.V. Sokolsky Institute of Fuel, Catalysis and Electrochemistry, Almaty[raushan.nurdillayeva@ayu.edu.kz](mailto:raushan.nurdillayeva@ayu.edu.kz), [bayeshov@mail.ru](mailto:bayeshov@mail.ru),[lazzat.sunatullaeva@ayu.edu.kz](mailto:lazzat.sunatullaeva@ayu.edu.kz), [gulkhan.zhylysbayeva@ayu.edu.kz](mailto:gulkhan.zhylysbayeva@ayu.edu.kz)**DISSOLUTION BEHAVIOR OF BRASS POLARIZED BY ALTERNATING CURRENT  
IN SODIUM PHOSPHATE AQUEOUS SOLUTION**

**Abstract.** The electrochemical behavior of Cu-Zn alloy (brass) polarized with industrial - frequency alternating current has been studied for the first time in aqueous sodium phosphate solution. The effects of current density in brass (200-1200 A/m<sup>2</sup>) and titanium (20-120 kA/m<sup>2</sup>) electrodes, sodium phosphate solution concentration (0,5-2,0 M), alternating current (AC) frequency (30-180 Hz) and electrolysis duration (0,25-1,5 h) on the alloy dissolution current efficiency were considered.

Intensive brass dissolution by forming copper (II) and zinc (II) ions during the electrolysis in alternating current mode was shown for the first time. In the case of direct current (DC) electrolysis, the current output value of alloy electrochemical dissolution was very low. As the current density of the alternating current polarized brass electrode was increased, the current output rate of the alloy dissolution increased initially and decreased to 400 A/m<sup>2</sup>, where (400 A/m<sup>2</sup>) alternating current value comprised 80% in an optimal condition. When the titanium electrode current density was increased, the brass dissolution current efficiency showed a maximum value; the current output of Cu (II) and Zn (II) ions formation at current 60 kA/m<sup>2</sup> density was 50% and 30%, respectively. As the electrolysis duration and the AC frequency are increased, the brass electrode current efficiency is reduced.

On the basis of obtained results, the potential of copper and zinc phosphate synthesis was shown.

**Key words:** brass, alternating current, electrolysis, sodium phosphate, titanium electrode.

At present, the use of alternating current in studying alloy electrochemical properties and in the synthesis of its important compounds is of great interest. Electrochemical processes are used to solve various topical issues in the field of production. Rather than direct current, alternating current allows to create simple, yet rational technological processes [1].

Alloys electrochemical dissolution is a very complicated process. An alloy of copper with zinc is called brass; by composition they may be red brass (containing less than 20% zinc), yellow brass (20-50% zinc), white brass (50-80% zinc) and special brass (containing lead, nickel manganese, iron, silicon, beryllium, etc. alongside with copper and zinc). The alloy electrochemical dissolution depends on dimensional ratio of its components and nature of the solution [2]. The more copper-based alloys are used, the more their residuals size in the environment increases as well. Digestion of metals from solid alloy wastes is an important source of production, since it reduces load on the environment [3, 4]. Subsequently, the demand for copper alloys, especially for brass (C38500) is great due to the development of automobile industry and the construction industry. Therefore, a thorough study of copper alloy properties is one of the main tasks today [5].

In this regard, it is important to develop different methods of processing solid alloy residuals on the basis of copper and zinc.

As the copper contains Cu 87%, Zn 13.67% and other impurities 0.33%, the brass electrochemical dissolution is similar to the copper electrochemical dissolution properties. Therefore, the copper electrochemical properties can be applied to the Cu-Zn alloy [2].

A.B. Bayeshov and et al. developed a method of obtaining copper (II) sulfate by the industrial alternating current polarization [6]; while the method of obtaining copper (I) chloride and copper bromide, inorganic copper and zinc compounds was developed by A.S. Kadirbayeva and R.N. Nurdillayeva [7-9].

With a view of obtaining copper salts, the electrochemical properties of copper were studied in sodium carbonate, sulfuric acid, potassium iodide, potassium bromide, and sodium sulfate, neutral and acidic media [10-15].

Corrosive [16-17] and electrochemical [18-21] properties of brass in aqueous solutions have been studied in a number of works. The electrochemical dissolution of brass was investigated by potentiodynamic polarization and cyclic voltammetry methods with and without the presence of Cl<sup>-</sup> ions in NaHSO<sub>3</sub> solution. The results of this work indicated that brass dissolution was accelerated by increasing HSO<sub>3</sub><sup>-</sup> concentration [18]. The electrochemical properties and passivation of Cu-30Zn alloy in the alkaline medium have been considered, increasing the NaOH concentration on the potentiodynamic curves basis has led to an increase in corrosion current density [19]. In the following study, the electrodisolution brass (60.8Cu-36.3Zn-2.9Pb) and pure copper were comparatively studied in 0.1 M HCl using cyclic voltammetry and a rotating ring-disc electrode and similarity of dissolution mechanism of copper and pure copper in the brass composition was discovered [20]. The electrochemical properties of α, β-brass (CuZn<sub>40</sub>Pb<sub>2</sub>) were investigated at different pH values in basic nitrate solutions. The study indicated that the extent of the dezincification was affected by presence of Pb in the alloy but the pH value was determined to be a key parameter [21].

Literature data show that brass electrode electrochemical properties in aqueous sodium phosphate solution have not been investigated.

### Results and discussion

In the present work, the brass electrode electrochemical properties were studied in aqueous sodium phosphate solution polarized with industrial-frequency alternating current. Due to the slow electrochemical reactions in the polarization of the brass electrode by direct current, an alternating current was used in our study. The achievement of using alternating current during the electrolysis was noted by the authors of [22] work.

During the alternating current polarization, the electrochemical dissolution of Cu-Zn alloy in the sodium phosphate aqueous solution was investigated at the range of 200 to 1200 A/m<sup>2</sup> (Fig. 1). When the current density is increased up to 400 A/m<sup>2</sup>, the current efficiency in Cu (II), Zn (II) ions formation and brass dissolution gradually increases. When the current density increased up to 1200 A/m<sup>2</sup>, the decrease in the alloy dissolution current output occurred. This can be explained by the increase in the additional reactions rate due to the current density increase.

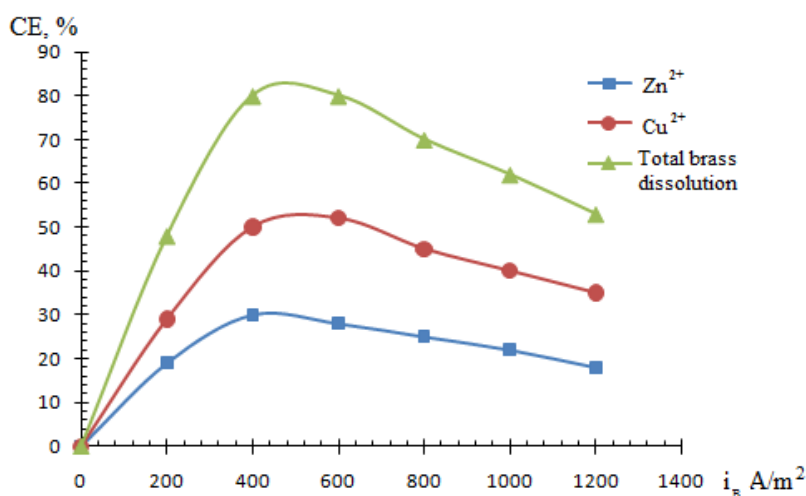


Figure 1 - The effect of the brass electrode current density on the current efficiency of the AC polarized Cu-Zn alloy dissolution:  $i_{T1}=60 \text{ kA/m}^2$ ,  $[\text{Na}_3\text{PO}_4]=1.0 \text{ M}$ ,  $\tau=0.5 \text{ h}$ .

The effect of the additional titanium electrode current density on the electrochemical dissolution of the brass electrode polarized with alternating current in a neutral medium was investigated (Figure 2). An increase in the current efficiency rate of Cu (II) ions formation and the total brass dissolution by increasing the current density of titanium electrodes from 20 kA/m<sup>2</sup> to 60 kA/m<sup>2</sup> can be explained by an occurrence of an oxide layer with a valve property on the titanium electrode surface in the anodic half-period. Further increase in the titanium electrode current density has led to a reduction in the current output. This is because the oxide layer surface structure in the titanium electrode changes due to the current density increase and its current correction property decreases.

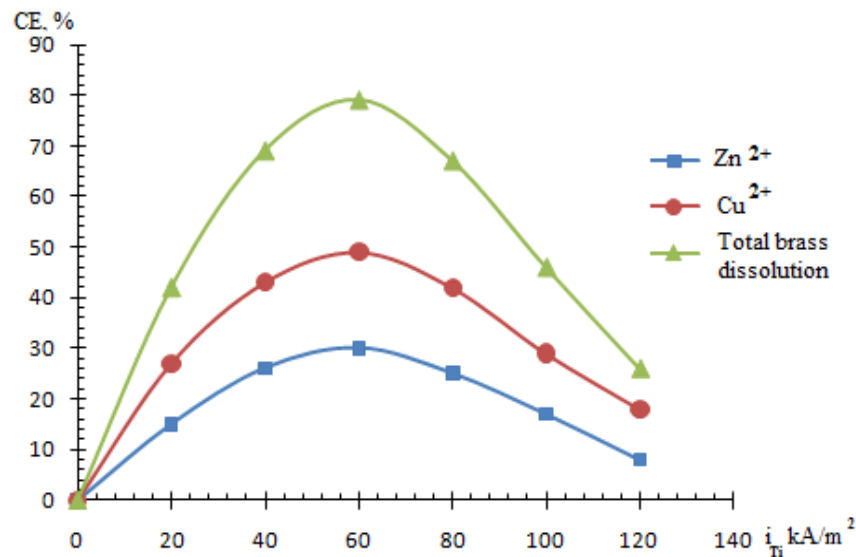


Figure 2 - Effect of titanium electrode current density on the current efficiency of the brass electrode dissolution polarized with alternating current:  $i_B=400$  A/m<sup>2</sup>,  $[Na_3PO_4]=1.0$  M,  $\tau=0.5$ h.

The effect of sodium phosphate solution concentration on the current efficiency of brass electrode dissolution polarized with alternating current was studied in a range 0.25 and 1.5 M (Fig. 3). As the sodium phosphate concentration increases, the current output of the brass electrode dissolution increases, but it decreases from 1.0 M. The reason is that as the electrolyte concentration increases, the brass electrode surface area is covered with saline coating and the brass electrode passivation takes place.

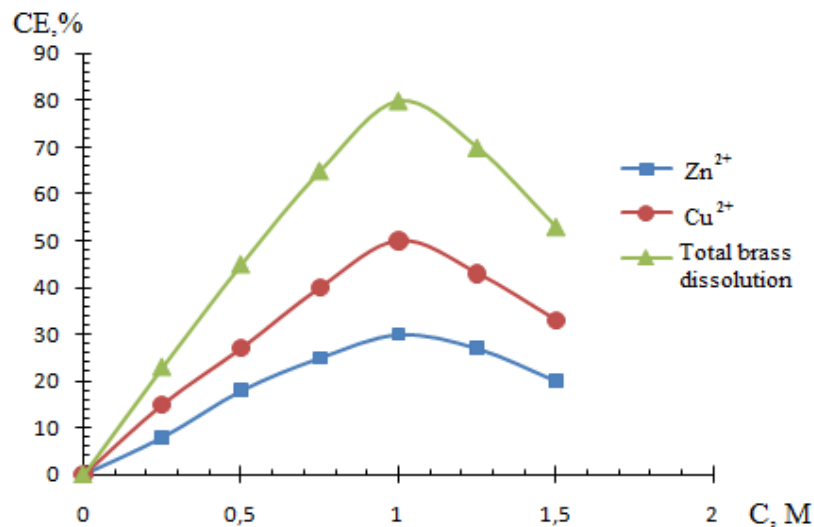


Figure 3 - Effect of sodium phosphate concentration on the current efficiency of brass electrode dissolution polarized with alternating current:  $i_{Ti} = 60$  kA/m<sup>2</sup>,  $i_B = 400$  A/m<sup>2</sup>,  $\tau = 0.5$ h.



The current efficiency decrease of copper, zinc ions formation and brass electrode dissolution due to the alternating current frequency increase can be observed in Figure 4. It can be assumed that the required time for the occurrence of the alloy oxidation reaction by forming copper and zinc ions can not be provided due to the rapid periods changes at high current frequencies.

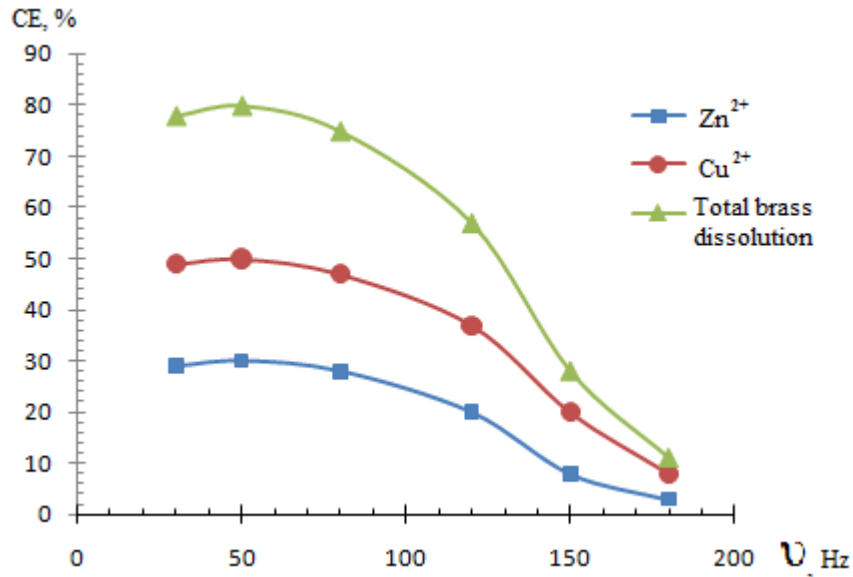


Figure 4 - AC frequencies effect on the current efficiency of brass electrode dissolution polarized with alternating current:  $i_{T1}=60$  kA/m<sup>2</sup>,  $i_B=400$  A/m<sup>2</sup>,  $[Na_3PO_4]=1.0$  M,  $\tau=0.5$  h.

Figure 5 shows the electrolysis duration effect on the brass electrode current current efficiency. As the, electrolysis duration increases, the brass electrode current output decreases. As the electrolysis duration increases, electrodes electrolysis products begin to passivate with poorly soluble copper and zinc products. It is explained by the formation of blue saline coat on the electrode surface.

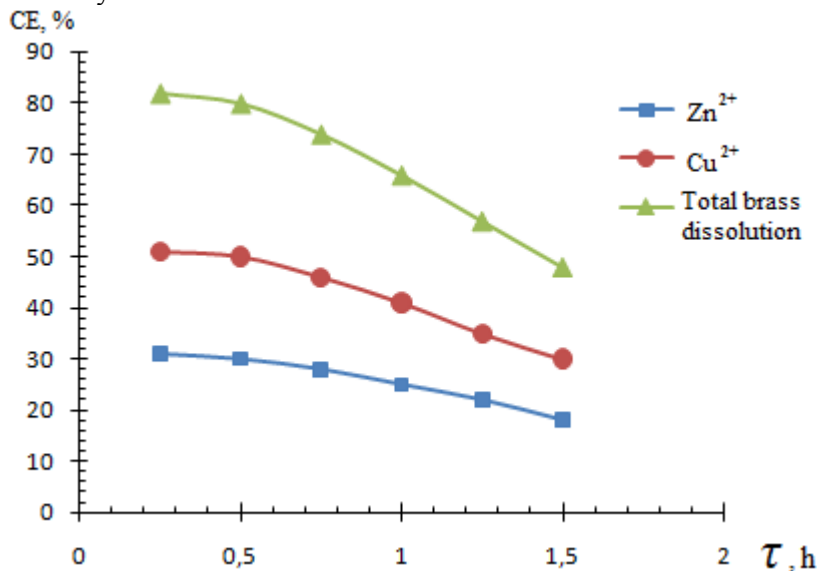


Figure 5 - The electrolysis duration effect on the current efficiency of brass electrode dissolution polarized with alternating current:  $i_{T1}=60$  A/m<sup>2</sup>,  $i_B=400$  A/m<sup>2</sup>,  $[Na_3PO_4]=1.0$  M

Figure 6 shows the solution temperature effect on the brass electrode current efficiency. In our study, a decrease in current efficiency value of Cu (II) ions formation beginning from 30 °C was observed due to the increase in electrolyte temperature and the linear increase in the current efficiency value of Zn (II) ions formation took place. As the solution temperature increases, zinc chemically interacts with the

hydrogen ions and thereby its ionization potential is facilitated. The total current output of the alloy dissolution increased up to 40 °C and slowed down at higher temperatures.

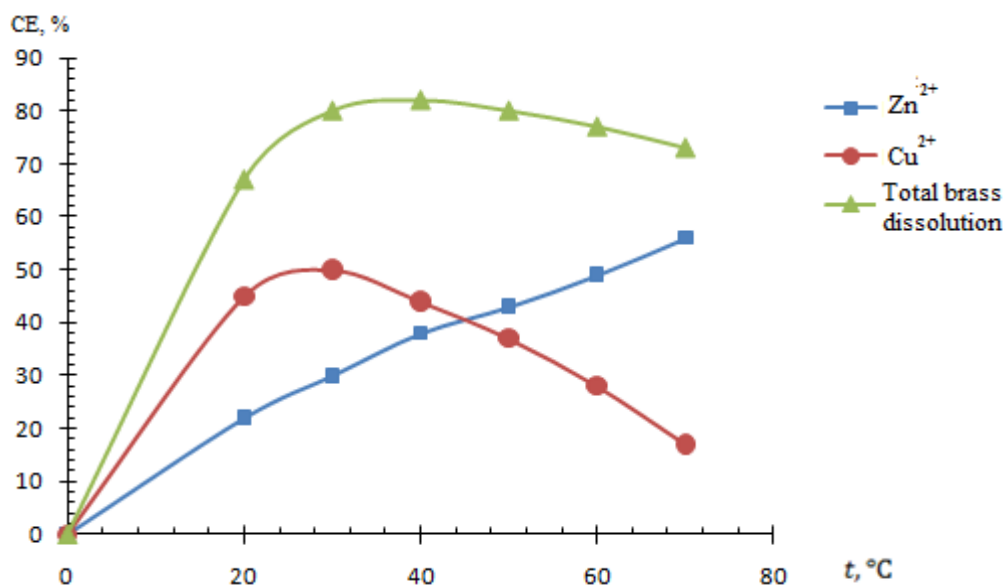


Figure 6 - The electrolyte temperature effect on the current efficiency of brass electrode dissolution polarized alternating current:  $i_{Ti}=60 \text{ A/m}^2$ ,  $i_B=400 \text{ A/m}^2$ ,  $[\text{Na}_3\text{PO}_4]=1.0 \text{ M}$ ,  $\tau=0.5 \text{ h}$ .

Summing up, the electrochemical dissolution laws of the brass electrode polarized with alternating current in a neutral medium - sodium phosphate aqueous solution have been systematically studied for the first time. The study results showed that the electrochemical process was intensified when replacing one of the two brass electrodes into the titanium wire. The basic electrochemical parameters effect on the brass electrode dissolution by forming copper and zinc ions in ( $\text{Na}_3\text{PO}_4$ ) sodium phosphate solution were investigated and the effective alloy dissolution conditions were considered: ( $i_B=400 \text{ A/m}^2$ ,  $i_{Ti}=60 \text{ kA/m}^2$ ,  $[\text{Na}_3\text{PO}_4]=1.0 \text{ M}$ ,  $\nu=50 \text{ Hz}$ ,  $t=30^\circ\text{C}$ ).

ӨОЖ 541.135.7:669.35'5

МРНТИ 31.15.33

Р.Н. Нүрділлаева<sup>1</sup>, А.Б. Басшов<sup>2</sup>, Л.А. Сунатуллаева<sup>1</sup>, Г.Н. Жылысбаева<sup>1</sup>

<sup>1</sup>Қожа Ахмет Ясауи атындағы Халықаралық қазақ-түрік университеті, Түркістан;

<sup>2</sup>Д.В.Сокольский атындағы Жанармай, катализ және электрохимия институты, Алматы

### АЙНЫМАЛЫ ТОКПЕН ПОЛЯРИЗАЦИЯЛАНҒАН ЖЕЗДІҢ НАТРИЙ ФОСФАТЫ СУЛЫ ЕРІТІНДІСІНДЕГІ ЕРУ ЗАҢДЫЛЫҚТАРЫ

**Аннотация.** Өндірістік жиіліктегі айнымалы токпен поляризацияланған Cu-Zn құймасы - жездің электрохимиялық қасиеті натрий фосфаты сулы ерітіндісінде алғаш рет зерттелді. Құйма еруінің ток бойынша шығымына (ТШ) жез ( $200-1200 \text{ A/m}^2$ ) және титан ( $20-120 \text{ kA/m}^2$ ) электродтарындағы ток тығыздықтарының, натрий фосфаты ерітіндісі концентрациясының ( $0,5-2,0 \text{ M}$ ), айнымалы ток жиілігінің ( $30-180 \text{ Гц}$ ), электролиз ұзақтығының ( $0,25-1,5 \text{ сағ.}$ ) әсерлері қарастырылды.

Айнымалы ток режиміндегі электролиз кезінде жездің мыс (II) және мырыш (II) иондарын түзе қарқынды еритіндігі алғаш рет көрсетілді. Ал, тұрақты ток электролиз барысында құйманың электрохимиялық еруінің ТШ мәні өте төмен болды. Айнымалы токпен поляризацияланған жез электродындағы ток тығыздығын жоғарылатқан сайын құйма еруінің ток бойынша шығымы алғашында жоғарылап,  $400 \text{ A/m}^2$ -бастап біркелкі төмендеп, оңтайлы жағдайда ( $400 \text{ A/m}^2$ ) ТШ мәні  $80\%$  құрады. Титан электродындағы ток тығыздығын арттырғанда құйма еруінің ТШ максимум арқылы өтіп, ток тығыздығы  $60 \text{ kA/m}^2$  кезінде Cu (II) және Zn (II) иондары түзілуінің ТШ сәйкесінше  $50\%$  және  $30\%$  құрады. Жез еруінің ток бойынша шығымы  $1,0 \text{ M}$  натрий фосфаты ерітіндісінде максимум мәнді көрсетті. Электролиз ұзақтығы

мен айнмалы ток жиілігін арттырған сайын жез электродының ток бойынша шығымы төмендейтіндігі анықталды.

Алынған нәтижелердің негізінде мыс және мырыш фосфатын синтездеудің мүмкіншіліктері көрсетілді.

**Түйін сөздер:** жез, айнмалы ток, электролиз, натрий фосфаты, титан электроды.

УДК 541.135.7:669.35'5

МРНТИ 31.15.33

**Р.Н. Нурдиллаева<sup>1</sup>, А.Б. Башов<sup>2</sup>, Л.А. Сунатуллаева<sup>1</sup>, Г.Н. Жылысбаева<sup>1</sup>**

<sup>1</sup>Международный казахско-турецкий университет им. Ходжи Ахмеда Ясави, Туркестан

<sup>2</sup>АО «Институт топлива, катализа и электрохимии им. Д.В.Сокольского», Алматы

### **ЗАКОНОМЕРНОСТИ РАСТВОРЕНИЯ ЛАТУНИ В ВОДНОМ РАСТВОРЕ ФОСФАТА НАТРИЯ ПРИ ПОЛЯРИЗАЦИИ ПЕРЕМЕННЫМ ТОКОМ**

**Аннотация.** Впервые исследовано электрохимическое поведение сплава Cu-Zn - латуни при поляризации переменным током промышленной частоты в водном растворе фосфата натрия. Рассмотрено влияние плотности тока на латунном электроде (200-1200 А/м<sup>2</sup>) и титановом электроде (20-120 кА/м<sup>2</sup>), концентрации раствора фосфата натрия (0,5-2,0 М), частоты переменного тока (30-150 Гц) и продолжительности электролиза (0,25-1,5 час) на выход по току (ВТ) растворения сплава.

Впервые показано, что при переменноточковом режиме электролиза происходит интенсивное растворение сплава с образованием ионов меди (II) и цинка (II). При электролизе с постоянным током значение ВТ электрохимического растворения сплава было значительно ниже. При повышении плотности тока на латунном электроде, поляризованном переменным током, выход по току растворения сплава плавно снижается и при оптимальных условиях (400 А/м<sup>2</sup>) значение ВТ составило 80%. При изменении плотности тока на титановом электроде ВТ растворения сплава проходит через максимум и ВТ образования ионов Cu (II) и Zn (II) составляет, соответственно, 50% и 30% при плотности тока 60 кА/м<sup>2</sup>.

Максимальное значение ВТ растворения латуни наблюдалось при 1,0 М концентрации раствора фосфата натрия. Установлено, что при увеличении продолжительности электролиза и частоты переменного тока значение ВТ латуни снижается.

На основе полученных результатов была показана возможность синтеза фосфатов меди и цинка.

**Ключевые слова:** латунь, переменный ток, электролиз, фосфат натрия, титановый электрод.

#### **Information about authors:**

R.N. Nurdillayeva – Khoja Akhmet Yassawi International Kazakh-Turkish University, Candidate of Chemistry Science (PhD), Associate Professor, E-mail: [raushan.nurdillayeva@ayu.edu.kz](mailto:raushan.nurdillayeva@ayu.edu.kz), <https://orcid.org/0000-0001-9444-737X>.

A.B. Bayeshov – «D.V.Sokolsky Institute of Fuel, Catalysis and Electrochemistry», Doctor of Chemistry Science, Professor, E-mail: [bayeshov@mail.ru](mailto:bayeshov@mail.ru), <https://orcid.org/0000-0003-0745-039X>.

L.A. Sunatullaeva – Khoja Akhmet Yassawi International Kazakh-Turkish University, master degree, II course, E-mail: [lazzat.sunatullaeva@ayu.edu.kz](mailto:lazzat.sunatullaeva@ayu.edu.kz), <https://orcid.org/0000-0002-0687-1021>

G.N. Zhylysbayeva – Khoja Akhmet Yassawi International Kazakh-Turkish University, Candidate of Technical Science (PhD), Associate Professor, E-mail: [gulkhan.zhylysbayeva@ayu.edu.kz](mailto:gulkhan.zhylysbayeva@ayu.edu.kz), <https://orcid.org/0000-0002-9800-3896>

#### **REFERENCES**

[1] Bayeshov A.B., Bayeshova A.K., Bayeshova C.A. (2014) Electrochemistry (theory and practice). [Elektrokhimiya (teoriyasi men koldaniui)]. Almaty: Kazakh university. - P. 316. ISBN 978-601-04-0671-1. (In Kazakh)

[2] Nurdillayeva R.N., Bayeshov A.B. (2007) Electrochemical dissolution kinetics and mechanism in copper sodium chloride solution [Zhezdin natrij hloridi eritindisindegi jelektrohimijalyk eru kinetikasy men mehanizmi]. NEWS of the Academy of Sciences of the Republic of Kazakhstan. Series Chemistry and Technology, Volume 5, №365. – P. 77-80. (In Kazakh)

[3] Bayeshov A.B., Bayeshova A.K. (2012) Electrochemical methods for the production of inorganic substances [Elektrohimicheskie sposoby polucheniya neorganicheskikh veshhestv]. Germaniya, Lambert, Academic Publishing. P. 72. ISBN 978-3-659-26096-4. (In Russian)

[4] James Evans, Lutgard De Jonghe. (2016) The Production and Processing of Inorganic Materials. Springer Nature, TMS.– P. 551. ISBN 978-3-319-48163-0. (In Eng)

[5] Sujit K.J., Devibala B., Rajalingam P. (2015) Experimental analysis of microstructure and mechanical properties of copper and brass based alloys. International Journal of Automotive and Mechanical Engineering (IJAME). ISSN 2229-8649 (Print); ISSN 2180-1606 (Online); Volume 11, P. 2317-2331. (In Eng)

- [6] Bayeshov A.B., Kadirbayeva A.S., Bayeshova A.K., Zhurinov M.Zh. (2014) Acquisition of copper (II) sulphate and chloride by the polarization of the production variable current. [Ondiristik ajnymaly tokpen poljarizacijalau arqyly mys (II) sul'fatyn zhane hlorldin alu.] ISSN 2224-5227.- Reports of the National Academy of Sciences of the Republic of Kazakhstan. №4, - P.24-28 (In Kazakh)
- [7] Kadirbayeva A.S., Nurdillayeva R.N. (2011) Acid copper (I) chloride by polarization of AC in hydrochloric acid solution [Tuz qyshqyly eritindisinde ajnymaly tokpen poljarizacijalau arqyly mys (I) hlorldin alu.] Bulletin of university Akhmet Yassawi., Series Chemistry and Technology, - P.103-108 (In Kazakh)
- [8] Nurdillayeva R.N., Bayeshov A.B., Serik G.S. (2018) The elaboration of copper bromide synthesis by electrochemical method. Bulletin of NAS RK. Volume 1, № 371, -P.73-80. ISSN 1991-3494. (In Eng)
- [9] Nurdillayeva R.N., Bayeshov A.B., Serik G.S., Bayeshova A.K. (2018) Production of copper bromide at polarization by an alternating current. News of the National Academy of Sciences of the RK, Series Chemistry and Technology, Volume 2, №428. P. 36-43. ISSN 2518-1491 (Online), ISSN 2224-5286 (Print). (In Eng)
- [10] Bayeshov A., Baiseitova A.A. (2005) The study of the processes of electrochemical dissolution of copper in a solution of sodium carbonate with polarization by alternating current [Izuchenie processov jelektrohimičeskogo rastvorenija medi v rastvore karbonate natrija pri poljarizacii peremennym tokom]. Reports of the National Academy of Sciences of the Republic of Kazakhstan. №4. -P.73 (In Russian)
- [11] Bayeshov A.B., Kadirbayeva A.S., Jurinov M.J. (2014) Dissolution of a copper electrode in sulfuric Acid at polarization by an industrial Alternating current. Int. J. Chem. Sci. Vol. 12, №3. - P. 1009-1014. ISSN 0972-768X. (In Eng)
- [12] Bayeshov A.B., Kadirbayeva A.S., Bayeshova A.K., Adaybekova A.A. (2015) Investigation of the electrochemical properties of copper electrode in potassium iodide solution by drawing potentiodynamic polarization curves [Kalij iodidi eritindisindegi mys jelektrodynynng jelektrohimičialyq qasietin potentsiodynamikalnyq poljarizacijalyq qisyqtar tysiuru arqyly zertteu] NEWS of the Academy of Sciences of the Republic of Kazakhstan. Series Chemistry and Technology. –№2. - P. 85-90. ISSN 2224-5227. (In Kazakh)
- [13] Bayeshova A.K., Kadirbayeva A.S., Bayeshov A.B. Adaybekova A.A. (2015) Electrochemical properties of copper in aqueous potassium bromide solution [Mystynng suly kalij bromidi eritindisindegi jelektrohimičialyq qasieti]. Reports of the National Academy of Sciences of the Republic of Kazakhstan. №2. -P. 46-52. ISSN 1991-3494. (In Kazakh)
- [14] Bayeshov A.B., Kadirbayeva A.S., Bayeshova A.K. (2015) Electrochemical properties of the polarized copper electrode in sodium sulphate solution of industrial variable current [Ondiristik ajnymaly tokpen poljarizacijalangan mys jelektrodynynng natrij sul'faty eritindisindegi jelektrohimičialyq qasietteri]. Proceedings of the VII International Scientific and Practical Conference on innovative development of oil and gas industry Almaty, –P. 409-413 (In Kazakh).
- [15] Bayeshov A.B., Kadirbayeva A.S., Bayeshova A.K. (2015) Electrochemical properties of polarized copper electrodes in neutral and acidic environments of industrial variable current [Ondiristik ajnymaly tokpen poljarizacijalangan mys jelektrodynynng bejtarap zhane qyshqyldy ortalardagy jelektrohimičialyq qasietteri] ISBN 2224-5227.- Reports of the National Academy of Sciences of the Republic of Kazakhstan. №3. -P. 18-23 (In Kazakh)
- [16] Kabasakaloğlu M., Kiyak T., Şendil O., Asan A. (2002) Electrochemical behavior of brass in 0.1 M NaCl. Applied Surface Science Volume 193, Issues 1–4, [https://doi.org/10.1016/S0169-4332\(02\)00258-1](https://doi.org/10.1016/S0169-4332(02)00258-1) P. 167-174 (in Eng)
- [17] Rotty C., Mandroyan A., Doche M.-L., Hihn J.Y (2016) Electropolishing of Cu-Zn brasses and 316L stainless steels: Influence of alloy composition or preparation process (ALM vs. standart metod). Surface & Coatings Technology. - P.125-135. <https://doi.org/10.1016/j.surfcoat.2016.08.076>. (in Eng)
- [18] Liu, Q., Luo, Hong Dong., Chunfeng Xiao, K li, Xiaogang. (2012). The Electrochemical Behaviour of Brass in NaHSO<sub>3</sub> Solution Without and With Cl<sup>-</sup>. International Journal of Electrochemical Science. 7. 11123-11136.
- [19] Arash F. A., Sajad A (2015) Electrochemical Behavior and Passivation of Cu–30Zn Alloy in Aqueous NaOH Solutions. Arab J Sci Eng (2015) 40:2993–2999 doi 10.1007/s13369-015-1788-5 Research article-Chemistry. (in Eng)
- [20] E. Geler, D.S. Azambuja. The electrochemical behavior of brass in 0.1 M HCl solution. [Journal of the Brazilian Chemical Society](https://doi.org/10.1590/S0103-50531997000200014). Print version ISSN 0103-5053. <http://dx.doi.org/10.1590/S0103-50531997000200014>
- [21] C. Berne, E. Andrieu, J. Reby, J-M. Sobrino, C. Blanc The Electrochemical Behavior of  $\alpha,\beta'$ -Brass in Basic NaNO<sub>3</sub> Solutions. This was Paper 726 and 758 presented at the Cancun, Mexico, Meeting of the Society, 2014.
- [22] A.B. Bayeshov, R.N. Nurdillayeva, Sh.H. Khabibullayeva (2019) Effect of the bromide ions on the titanium electrode dissolution polarized by alternating current in aqueous solutions. News of the Academy of Sciences of the Republic of Kazakhstan. Series Chemistry and Technology. №2. (In Eng) <https://doi.org/10.32014/2019.2518-1491.21>

## **Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan**

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct ([http://publicationethics.org/files/u2/New\\_Code.pdf](http://publicationethics.org/files/u2/New_Code.pdf)). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации  
в журнале смотреть на сайте:

[www.nauka-nanrk.kz](http://www.nauka-nanrk.kz)

<http://chemistry-technology.kz/index.php/en/arhiv>

**ISSN 2518-1491 (Online), ISSN 2224-5286 (Print)**

Редакторы: *М. С. Ахметова, Т. А. Апендиев, Аленов Д. С.*  
Верстка на компьютере *А. М. Кульгинбаевой*

Подписано в печать 05.06.2019.  
Формат 60x881/8. Бумага офсетная. Печать – ризограф.  
5.7 п.л. Тираж 300. Заказ 3.