

**ISSN 2518-1491 (Online),
ISSN 2224-5286 (Print)**

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ГЫЛЫМ АКАДЕМИЯСЫНЫҢ

Д.В.Сокольский атындағы «Жанармай,
катализ және электрохимия институты» АҚ

Х А Б А Р Л А Р Ы

ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК
РЕСПУБЛИКИ КАЗАХСТАН
АО «Институт топлива, катализа и
электрохимии им. Д.В. Сокольского»

N E W S

OF THE ACADEMY OF SCIENCES
OF THE REPUBLIC OF KAZAKHSTAN
JSC «D.V. Sokolsky institute of fuel, catalysis
and electrochemistry»

**SERIES
CHEMISTRY AND TECHNOLOGY**

6 (438)

NOVEMBER – DECEMBER 2019

PUBLISHED SINCE JANUARY 1947

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

NAS RK is pleased to announce that News of NAS RK. Series of chemistry and technologies scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of chemistry and technologies in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of chemical sciences to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Химия және технология сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруды. Web of Science зерттеушілер, авторлар, баспашилар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Химия және технология сериясы Emerging Sources Citation Index-ке енүі біздің қоғамдастық үшін ең өзекті және беделді химиялық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия химии и технологий» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по химическим наукам для нашего сообщества.

Бас редакторы
х.ғ.д., проф., ҚР ҮҒА академигі **М.Ж. Жұрынов**

Редакция алқасы:

Агабеков В.Е. проф., академик (Белорус)
Волков С.В. проф., академик (Украина)
Воротынцев М.А. проф., академик (Ресей)
Газалиев А.М. проф., академик (Қазақстан)
Ергожин Е.Е. проф., академик (Қазақстан)
Жармағамбетова А.К. проф. (Қазақстан), бас ред. орынбасары
Жоробекова Ш.Ж. проф., академик (Қырғыстан)
Иткулова Ш.С. проф. (Қазақстан)
Манташян А.А. проф., академик (Армения)
Пралиев К.Д. проф., академик (Қазақстан)
Баешов А.Б. проф., академик (Қазақстан)
Бұркітбаев М.М. проф., академик (Қазақстан)
Джусипбеков У.Ж. проф. корр.-мүшесі (Қазақстан)
Молдахметов М.З. проф., академик (Қазақстан)
Мансуров З.А. проф. (Қазақстан)
Наурызбаев М.К. проф. (Қазақстан)
Рудик В. проф., академик (Молдова)
Рахимов К.Д. проф. академик (Қазақстан)
Стрельцов Е. проф. (Белорус)
Тәшімов Л.Т. проф., академик (Қазақстан)
Тодераш И. проф., академик (Молдова)
Халиков Д.Х. проф., академик (Тәжікстан)
Фарзалиев В. проф., академик (Әзірбайжан)

«ҚР ҮҒА Хабарлары. Химия және технология сериясы».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Меншіктенуші: «Қазақстан Республикасының Үлттық ғылым академиясы» Республикалық қоғамдық бірлестігі (Алматы қ.)

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде 30.04.2010 ж. берілген №1089-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,
<http://chemistry-technology.kz/index.php/en/archiv>

© Қазақстан Республикасының Үлттық ғылым академиясы, 2019

Типографияның мекенжайы: «Аруна» ЖК, Алматы қ., Муратбаева көш., 75.

Г л а в н ы й р е д а к т о р
д.х.н., проф., академик НАН РК **М. Ж. Журинов**

Р е д а к ц и о н н а я к о л л е г и я:

Агабеков В.Е. проф., академик (Беларусь)
Волков С.В. проф., академик (Украина)
Воротынцев М.А. проф., академик (Россия)
Газалиев А.М. проф., академик (Казахстан)
Ергожин Е.Е. проф., академик (Казахстан)
Жармагамбетова А.К. проф. (Казахстан), зам. гл. ред.
Жоробекова Ш.Ж. проф., академик (Кыргызстан)
Иткулова Ш.С. проф. (Казахстан)
Манташян А.А. проф., академик (Армения)
Пралиев К.Д. проф., академик (Казахстан)
Баешов А.Б. проф., академик (Казахстан)
Буркитбаев М.М. проф., академик (Казахстан)
Джусипбеков У.Ж. проф. чл.-корр. (Казахстан)
Мулдахметов М.З. проф., академик (Казахстан)
Мансуров З.А. проф. (Казахстан)
Наурызбаев М.К. проф. (Казахстан)
Рудик В. проф., академик (Молдова)
Рахимов К.Д. проф. академик (Казахстан)
Стрельцов Е. проф. (Беларусь)
Ташимов Л.Т. проф., академик (Казахстан)
Тодераш И. проф., академик (Молдова)
Халиков Д.Х. проф., академик (Таджикистан)
Фарзалиев В. проф., академик (Азербайджан)

«Известия НАН РК. Серия химии и технологии».

ISSN 2518-1491 (Online),

ISSN 2224-5286 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан» (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10893-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел. 272-13-19, 272-13-18,

<http://chemistry-technology.kz/index.php/en/arhiv>

© Национальная академия наук Республики Казахстан, 2019

Адрес редакции: 050100, г. Алматы, ул. Кунаева, 142,
Институт органического катализа и электрохимии им. Д. В. Сокольского,
каб. 310, тел. 291-62-80, факс 291-57-22, e-mail:orgcat@nursat.kz

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75

NEWS

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

SERIES CHEMISTRY AND TECHNOLOGY

ISSN 2224-5286

<https://doi.org/10.32014/2019.2518-1491.72>

Volume 6, Number 438 (2019), 42 – 48

UDK 541.64+678

**Zh.B. Rakhimberlinova¹, G.A. Mustafina², A.T. Takibayeva¹,
I.V. Kulakov³, A.R. Iskakov¹, O.G. Nazarova¹**

¹Karaganda State Technical University, Karaganda, Kazakhstan;

²LP «KAZ-OPTIMUM», Karaganda, Kazakhstan;

³Tyumen State University, Tyumen, Russia

E-mail:kargtu_tss@mail.ru

SYNTHEZIZING NITRILE-CONTAINING GLYCONITRILE (CO) POLYMERS

Abstract. The article presents the results of studying the production of new nitrile-containing monomers by acylation of unsaturated N- and N,N' - α -aminoacetonitrile chlorides (meta) acrylic acids using acrylamide. The initial unsaturated N- and N,N' - α -aminoacetonitriles were synthesized by interaction of glycolic acid nitrile (glyconitrile) with amines of various classes. The ability of new monomers to radical (co)polymerization was studied, namely, the possibility of producing polyacrylamides based on N,N' nitrile derivatives of (meta) acrylamide and vinyl ester (N - acetonitrile) monoethanolamine (VEEAN) with acrylamide in bulk in the presence of radical initiators and organic solvents with formation of carbochain polymers. The formation of nitrile-containing polyacrylamides is confirmed by the data of the elemental analysis, viscometry, IR spectroscopy. Viscometric data $[\eta] = 0.10 - 0.29 \text{ dl/g}$ of polymers indicate low reactivity of the synthesized nitrile acrylamides compared to acrylamide that is associated with the steric effect of the chain length. The synthesized copolymers were studied as modifiers of urea-formaldehyde binders (UFB) used to strengthen unstable rocks. The samples strengthened with UFB solutions without a modifier showed low strength indices for 62 and 77 % concentrations, respectively, while introduction of nitrile-containing copolymers in the amount of 1-5 % wt. improved strength characteristics of the samples by 1.2-1.8 times. The good strength results for mine rocks are explained by the increased flexibility and elasticity of the urea-formaldehyde binder chains with new functional groups responsible for the resin adhesion to the rock.

Keywords: α -aminoacetonitriles, glycolic acid nitrile (glyconitrile), monoethanolamine vinyl ester, acrylamide, polyacrylamide, N,N'- acrylamide nitrile derivatives, copolymers, urea-formaldehyde binder modifiers.

Introduction

Recently the scientific and practical interest in the directed synthesis of nitrile-containing polyfunctional polymers has been steadily growing. This is caused by a wide range of useful properties of these (co)polymers that can be further used as promising flocculants, coagulants, polyelectrolytes, modifiers for urea binders, semi-synthetic soil structures. Great prospects in this direction are opened by studying the interaction of glyconitrile with various compounds caused by its extremely high reactivity and associated with it rich possibility of obtaining a wide variety of organic compounds. Among the variety of compounds synthesized from glyconitrile, the most interesting are its N- and N,N'- α -amino derivatives, which is associated with the ease of their preparation, the possibility of chemical transformations and their practical significance. Many of them can be proposed as polyfunctional monomers for polymerization or polycondensation, which will allow obtaining new types of interesting polymers both in practical and in scientific terms.

Nitrile-containing polyfunctional polymers described in the article were obtained by joint radical (co)polymerization of monomers of nitrile derivatives N,N'- (meta) acrylamide that were synthesized by acylation of unsaturated N- and N,N' - α -aminoacetonitriles (meta) acrylic acids, acrylates.

The obtained (co)polymers based on derivatives of glycolic acid nitrile are assigned to carbochain polymers of linear structure with long side groups. New nitrile-containing (co)polymers are characterized by a low molecular weight and a significant number of functional groups capable of further transformations and predetermining various fields of their application [1-2].

Experimental Part

Synthesizing α -aminoacetonitriles (I-VI)

Aminoacetonitrile NH_2CH_2CN (I). 16 ml of the 70% aqueous glyconitrile solution (0.2 mol) are added dropwise to 13.6 ml of the 23% aqueous ammonia solution (0.2 mol) with cooling at the temperature of 0-5 °C so that the temperature of the reaction mixture does not exceed 10 °C. After that, the synthesis temperature is raised to the room temperature and held within 1.5 hours. 20 ml of concentrated HCl (0.2 mol) are added to the reaction mixture. The mixture containing aminoacetonitrile in the form of hydrochloric acid salt is evaporated. $HCl \cdot NH_2 \cdot CH_2 \cdot CN$ crystals are washed with ester and dried.

N-methylaminoacetonitrile CH_3NHCH_2CN (II). The synthesis is carried out analogously to (I) with 2 moles of amine. At the end of the synthesis, the reaction mixture is saturated with sodium sulfate and extracted repeatedly with diethyl ester. The solvent is distilled off, the residue is subjected to vacuum distillation.

N-allylaminocetone $CH_2=CH-CH_2-NH-CH_2CN$ (III). To 22.8 ml of the 50 % aqueous solution of allylamine (0.2 mol) there are added dropwise 16 ml of the 70 % aqueous solution of glyconitrile (0.2 mol) while the reaction mixture is cooled to 5 °C. Upon completion of adding the glyconitrile solution, the mixture is heated to 35 °C and kept at this temperature within 2 hours. The separated oil layer of aminonitrile is separated from the aqueous solution using a separatory funnel. An additional amount of aminonitrile is extracted from the aqueous layer with diethyl ester. The ester extract and the organic layer are mixed, dried over anhydrous sodium sulfate, diethyl ester is distilled off, the residue is subjected to vacuum fractional distillation.

Vinyl ester of (-N-acetonitrile)-ethanolamine $CH_2=CH-O-CH_2CH_2NH-CH_2CN$ (IV). The synthesis is carried out similarly to (III) with 0.2 moles of amine at 35-40 °C.

N-benzylaminoacetonitrile $C_6H_5CH_2NHCH_2CN$ (V-VI). The synthesis is carried out similarly to (III) with 0.2 moles of amine at 35-40 °C (Table 1).

Table 1 - Synthesizing α – aminoacetonitrile – $RHNCH_2CN$

Compounds	R	Yield, %	T _{boil} , °C	d ₄ ²⁰	n _D ²⁰
I	H	80	T _{mel} 165-166	-	-
II	CH ₃	65	45/0.4	0.9300	1.4199
III	CH ₂ =CH-CH ₂	78	85-88/0.4	0.9281	1.4486
IV	CH ₂ =CH-CH- —O—CH ₂ —CH ₂	90	91-93/0.4	1.0060	1.4691
V	C ₆ H ₅ CH ₂	90	130-133/0.4	1.0460	1.5388
VI	C ₆ H ₅	50	145/1	-	-

Synthesizing N,N'-derivatives of glycolic acid nitrile (VII-XI)

N,N'-substituted acrylamides: a) a mixture of 200 ml of benzene (diethyl ester or acetone), 7 g of dry K₂CO₃ and 0.2 mol of α -aminoacetonitrile is cooled to 8-10 °C, a solution of 0.2 mol of acrylic acid chloride is added dropwise in 60 ml of benzene (diethyl ester or acetone) at such a rate that the temperature of the reaction mixture does not exceed 10 °C. After 45 minutes, another 7 g of dry K₂CO₃ are added and stirred within 1 hour at 10 °C, then 1 hour at the room temperature. The inorganic precipitate is filtered off, washed twice with 60 ml of hot benzene (diethyl ester or acetone). The solvent is distilled off, the residue containing nitrile-substituted acrylamide is subjected to fractional vacuum distillation in the presence of the copper chip polymerization inhibitor (Table 2).

b) In the aqueous medium synthesizing N,N'-substituted acrylamides is carried out according to the following procedure: an equimolar amount of acrylic acid chloride in benzene and the 50 % aqueous


NaOH solution are added from two dropping funnels to the reaction mixture of α -aminoacetonitriles obtained by the above procedure II-VI with vigorous stirring and cooling (-5 °C). Then the reaction mixture is kept within 1 hour at the room temperature. The final product is extracted with benzene, the solvent is distilled off, nitrile-substituted acrylamide is subjected to vacuum distillation. Their characteristics are given in Table 2.

Table 2 –Characteristics of N,N'-substituted acrylamides

Compound No.	R	R'	Yield, g	T _{boil} , °C; 0,4 MPa
VII	CH ₃	H	15.0 (54)	115-118
VIII	CH ₃	CH ₃	19.0 (75)	117-120
VIII	CH ₃	CH ₃	20.3 (80)*	117-120
IX	CH ₂ =CH-O-CH ₂ CH ₂	H	19.0 (62)	140-142
X	CH ₂ =CH-O-CH ₂ CH ₂	CH ₃	30.6 (90)	147-149
XI	CH ₂ =CH-O-CH ₂ CH ₂	CH ₃	28.0 (85)*	147-149


*-in the aqueous medium

Homopolymer of N,N'-derivatives of acrylamide (XII)




The synthesis is carried out by radical polymerization in bulk or in dimethylformamide (DMF) in the presence of radical initiators: dinitrile azobisisobutyric acid (DAA) or benzoyl peroxide in the amount of 0.5-1 % of the total weight of the monomer at 70 % within 6-10 hours, in argon atmosphere. The copolymers obtained are reprecipitated from solutions in dioxane, acetone, dimethylformamide (DMF), water or methanol and dried at the room temperature in a vacuum oven to the constant weight.

(-N-acetonitrile) ethanolamine vinyl ester copolymers (XIII)



a) with alkyl acrylates (R = -OR', where R'-CH₃-; C₂H₅-; C₄H₉-) are obtained in bulk in the presence of 0.5 % DAA at various ratios of monomers, the synthesis temperature is 70 °C, and the duration is 6 hours. The copolymers are reprecipitated according to procedure (1);

b) with acrylamide:




is obtained by copolymerization of components in DMF, in the presence of DAA in the amount of 0.5 % of the monomer weight at the temperature of 70 °C within 6 hours, the ratio of the starting reagents is equimolar. The copolymers are reprecipitated according to procedure (1).

Urea-formaldehyde binders UFB modifications (XIV–XV). Synthesized copolymer (XII) was diluted with water-dioxane (2:1) to the 50 % concentration, the specific gravity of the solution was 1.078 g/cm³, and copolymer (XIII) was diluted to the 70 % concentration with the specific gravity of 1.073 g/cm³.

Results and discussion

The subject of our studies were copolymers and polymers of nitrile derivatives of N,N'(meta) acrylamide with acrylamide that were studied as new modifiers for urea binders used to strengthen unstable rocks, semi-synthetic soil structures, foaming agents in flotation concentration of sulfide copper ores.

Unsaturated N- and N,N'- α -aminoacetonitriles were used as starting monomers for synthesizing the above polymers. The synthesis of α -aminoacetonitriles is based on the reaction of glycolic acid nitrile (glyconitrile) interaction with amines of various classes according to the scheme:




where R and R' are alkyl, aryl, alkenyl, heterocycle.

The specific structure of glyconitrile, namely, the close proximity of OH and CN - groups determines the features of its interaction with primary and secondary amines. The synthesis of glyconitrile with amines was studied at the equimolar ratio of the starting reagents, various temperatures, durations, solvents, and the concentration of the starting reagents. The optimum process parameters were found (40-60 °C, 1-2 hours, amine concentration 50-100 %, glyconitrile concentration 50-70 %, water). Above 60 °C side reactions begin to occur with participation of C≡N and NH - groups of products of imines or resins formation. In organic solvents the yield of final products is significantly reduced.

Their structure is confirmed by the data of the elemental analysis, IR and NMR spectra. IR spectra of aminonitriles are characterized by the presence of a number of absorption bands, groups: 2250 - 2240 cm⁻¹ - C≡N; 3400 - 3320 cm⁻¹ - NH; 1640 cm⁻¹ - CH₂=CH- .

The new N,N' derivatives of acrylamide were synthesized by acylation of unsaturated R- α -aminoacetonitriles obtained by the above procedure with (meta) acrylic acid chlorides:




where R = H, - NH-CH₂CH₂OCH=CH₂; R' = H, - CH₃.

The physical-and-chemical constants of the obtained N,N'-derivatives of acrylamide are presented in Table 2. Their composition and structure were confirmed by the elemental analysis, IR and NMR spectra.


The IR spectra of these compounds contain absorption bands in the region of 2300 cm⁻¹ (nitrile group), 1650-1680 cm⁻¹ (amide group), 1800-1860 cm⁻¹ (vinyl group). The NMR spectra show absorption bands of methylene protons of the - CH₂CN group (region 4.26-4.67 ppm) and vinyl protons at 5.9-6.9 ppm and 5.25-6.03 ppm.

We investigated the possibility of producing polymers based on N,N'- nitrile derivatives of (meta) acrylamide and vinyl ester (N - acetonitrile) - monoethanolamine (VEEAN) with acrylamide with formation of carbochain polymers of the following structure:

- copolymers of N,N'- nitrile derivatives (meta) of acrylamide with acrylamide:

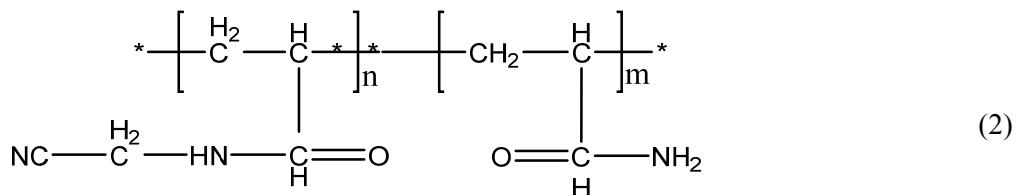

- copolymer of vinyl ester (N-acetonitrile)-ethanolamine with acrylamide

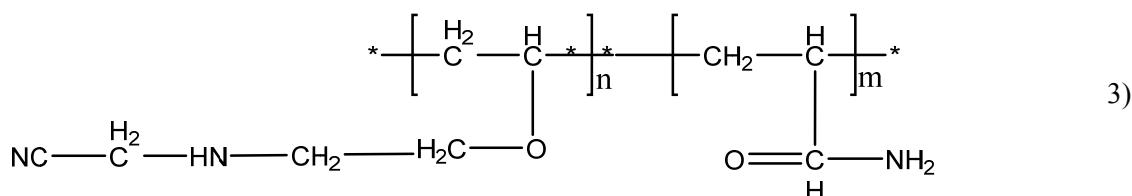

The viscometric data $[\eta] = 0.10 - 0.29 \text{ dl/g}$ of polymers indicate low reactivity of the synthesized nitriacrylamides compared to acrylamide that is associated with the steric effect of the long chain and the nature of the R_1 substituent. For the obtained polymers, an anomalous dependence of viscosity on solution concentration is observed, which is associated with the presence of ionogenic groups in the composition. It allows attributing them to polyelectrolytes.

The synthesized copolymers were investigated as modifiers for urea binders (UFB) used to strengthen unstable rocks.

Modification was carried out by combining aqueous solutions of UFB with the copolymers taken in the amount of 1-5 % of the UFB weight. It was noted that copolymers combine well with UFB and do not stratify over time. The presence of active functional groups ($\text{CO} =$, $\text{C}\equiv\text{N}$, NH_2 , $-\text{C}-\text{O}$, CONH_2) in the modifiers contributed to increasing the adhesive ability.

In order to establish the modifying effect of the copolymers based on synthesized (co)polymers for compressive strength, the mixtures with a hardener, oxalic acid, and with a filler, ground mine rock, represented by medium strength mudstone, were compiled. The resin to rock ratio was 1: 6, the mixture was loaded into molds and pressed at 10 atm within 3 minutes. Testing the strengthened samples for compressive strength was carried out after 7 and 21 days of storage in the air at 15 °C. The results of testing the rock samples reinforced with modified solutions of UFB depending on the concentration of resin and modifier are presented in Table 3.

Table 3 - The use of polymers based on copolymers of nitrile derivatives of $\text{N},\text{N}'(\text{meta})$ acrylamide with acrylamide as binders for mine rocks

No.	Modifier	Concentration, %	Modifier concentration %	Compression strength of the samples, kp/cm ²	
				Storage time	days
				7	21
	UFB without a modifier	77	0	18.4	31.1
XIV	(N-acetonitrile)-ethanolamine vinyl ester copolymer with acrylamide	77	1	26.9	41.0
		77	3	-	38.2
		77	5	-	39.6
		62	5	19.8	26.9
XV	Methylacetonitrile acrylamide copolymer with acrylamide	77	-	-	53.8
		77	3	-	56.6
		77	5	-	56.6
		62	5	-	26.2

From the data of Table 3 it follows that the samples strengthened with UFB solutions without a modifier have low strength indicators for 62 and 77 % concentration, respectively. The introduction of nitrile-containing copolymers in the amount of 1-5 % wt. increases the strengthened samples strength by 1.2-1.8 times in comparison with the samples strengthened with unmodified UFB. It has been shown that with decreasing the concentration of UFB in the binder, the samples strength decreases. Increasing the modifier concentration from 1 to 5 % wt. does not lead to a substantial increase in strength properties.

Conclusions

Thus, as a result of studies performed, by the acylation reaction of N- and N,N' - α - aminoacetonitrile chlorides of (meta)acrylic acids with acrylamide, new monomers of (meta)acrylamide were obtained and characterized. The initial unsaturated N- and N,N' - α - aminoacetonitriles were synthesized by the interaction of glycolic acid nitrile (glyconitrile) with amines of various classes. The ability of new monomers to radical (co)polymerization in bulk and in organic solvents with formation of nitrile-containing polyacrylamides has been shown.

According to the results of laboratory tests, the synthesized copolymers have shown that they are good binders for mine rocks, providing relatively high mechanical strength compared to unmodified binders. The strengthening effect of modifiers is caused by increasing the flexibility and elasticity of urea-formaldehyde binder chains (UFB) with the advent of new functional groups $\text{CO} =$; $\text{C}\equiv\text{N}$; CONH_2 ; $\text{C}-\text{O}-\text{C}$ that are responsible for the resin adhesion to the rock.

**Ж.Б. Рахимберлинова¹, Г.А. Мустафина², А.Т. Такибаева¹,
И.В. Кулаков³, А. Р. Исаков¹, О.Г. Назарова¹**

¹Қарағанды мемлекеттік техникалық университеті, Қарағанды, Қазақстан;

²ЖШС «KAZ-OPTIMUM», Қарағанды, Қазақстан;

³Тюмень мемлекеттік университеті, Тюмень, Ресей

НИТРИЛ ҚҰРАМДЫ ГЛИКОНИТРИЛ СО ПОЛИМЕРЛЕРІНІҢ СИНТЕЗІ

Аннотация. Мақалада N - и N,N' - α - аминоацетонитрилдерді хлорангидридтермен (мета) акрил қышқылдарымен, акриламидпен ацилдеу жолымен жаңа нитрил бар мономерлерді алууды зерттеу нәтижелері көлтірілген. Бастапқы құтпеген N - және N,N' - α - аминоацетонитрилдер әртүрлі класты аминдермен гликоль қышқылы (гликонитрил) нитрилінің өзара әрекеттесуімен синтезделген. Жаңа мономерлердің радикалды (со)полимерлеуге қабілеттілігі зерттелді, атап айтқанда N,N' – нитрил туынды (мета) акриламид пен винил эфири (N – ацетонитрил) моноэтоламин (ВЭЭАН) негізінде радикалды бастамашылардың қатысуымен және карбоцепті полимерлер түзілетін органикалық еріткіштерде акриламидпен полиакриламид алу мүмкіндігі зерттелді. Құрамында нитрил бар полиакриламидтердің түзілуі элементтік талдау, вискозиметрия, ИК – спектроскопия деректерімен расталған. [η] = 0,10 - 0,29 дL/g полимерлердің вискозиметриялық деректері синтезделген нитрилакриламидтердің акриламидпен салыстырғанда реакциялық кабілеттінің төмендігін көрсетеді, бұл тізбек ұзындығының стерильді әсерімен байланысты. Синтезделген сополимерлер тұрақсыз тау жыныстарын нығайту үшін пайдаланылатын мочевино-формальдегидті байланыстырығыш (МФС) модификаторлар ретінде зерттелді. Модификаторсыз МФС ерітіндісімен бекітілген үлгілер 62 және 77% концентрацияға арналған төмен беріктік көрсеткіштерін көрсетті, 1-5% салмақ мөлшерінде нитрил бар сополимерлерді енгізу. үлгілердің беріктігін 1,2-1,8 есеге жақсартты. Шахталық жыныстар үшін беріктік көрсеткіштері бойынша жақсы нәтижелер шайырдың жынысқа адгезиясына жауапты жаңа функционалдық топтармен несепнәрформальдегидті байланыстыруышы тізбектерінің икемділігі мен икемділігінің артуымен түсіндіріледі.

Түйін сөздер: α –аминоацетонитрилдер, гликоль қышқылының нитрилі (гликонитрил), моноэтаноламин винил эфири, акриламид, полиакриламид, N, N' – нитрил туынды акриламид, сополимерлер, мочевино-формальдегидті байланыстырығыштардың модификаторлары.

**Ж.Б. Рахимберлинова¹, Г.А. Мустафина², А.Т. Такибаева¹,
И.В. Кулаков³, А. Р. Исаков¹, О.Г. Назарова¹**

¹Қарагандинский государственный технический университет, Караганда, Казахстан;

²ТОО «KAZ-OPTIMUM», Караганда, Казахстан;

³Тюменский государственный университет, Тюмень, Россия

СИНТЕЗ НИТРИЛСОДЕРЖАЩИХ (СО) ПОЛИМЕРОВ ГЛИКОНИТРИЛА

Аннотация. В статье приведены результаты исследований получения новых нитрилсодержащих мономеров путем ацилирования непредельных N- и N,N' - α - аминоацетонитрилов хлорангидридами (мета) акриловых кислот, акриламидом. Исходные непредельные N- и N,N' - α - аминоацетонитрилы синтезированы взаимодействием нитрила гликоловой кислоты (гликонитрила) с аминами различного класса. Изучена способность новых мономеров к радикальной (со)полимеризации, а именно возможность получения полиакриламидов на основе N,N' – нитрилпроизводных (мета) акриламида и винилового эфира (N – ацетонитрил) моноэтоламина (ВЭЭАН) с акриламидом в массе в присутствии радикальных инициаторов и органических растворителей с образованием карбоцепных полимеров. Образование нитрилсодержащих полиакриламидов подтверждено данными элементного анализа, вискозиметрии, ИК – спектроскопии. Вискозиметрические данные [η] = 0,10 – 0,29 дL/g полимеров свидетельствуют о невысокой реакционной способности синтезированных нитрилакриламидов по сравнению с акриламидом, что связано с стерическим влиянием длины цепи. Синтезированные сополимеры были исследованы в качестве модификаторов мочевино-формальдегидных связующих (МФС), используемых для укрепления неустойчивых горных пород. Образцы, укрепленные растворами МФС без модификатора, показали низкие прочностные показатели для 62 и 77% концентрации соответственно, введение же нитрилсодержащих сополимеров в количестве 1-5% вес. улучшили прочностные характеристики образцов в 1,2-1,8 раза. Хорошие результаты по прочностным показателям для шахтных пород объясняется увеличением гибкости и эластичности цепей

мочевиноформальдегидных связующих новыми функциональными группами, ответственных за адгезию смолы к породе.

Ключевые слова: α – аминоацетонитрилы, нитрил гликоловой кислоты (гликонитрил), виниловый эфир моноэтаноламина, акриламид, поликариламид, N,N' – нитрилпроизводные акриламида, сополимеры, модификаторы мочевин-формальдегидных связующих.

Information about the authors:

Rakhimberlinova Zh.B. – Candidate of Chemical Sciences, Karaganda State Technical University, e-mail:kargtu_tss@mail.ru, orcid.org/0000-0002-3326-0998

Mustafina G.A. - Candidate of Chemical Sciences, LTD «KAZ-OPTIMUM», e-mail: gmustafina@list.ru, orcid.org/0000-0001-7265-2524

Takibayeva A.T. – Candidate of Chemical Sciences, Karaganda State Technical University, e-mail: altynarai81@mail.ru, orcid.org/0000-0003-0536-0817

Kulakov I.V. – Candidate of Chemical Sciences, Tyumen State University, e-mail: ivankul@mail.ru, orcid.org/0000-0001-5772-2096.

Iskakov A.R. – Master student, Karaganda State Technical University, e-mail: arnur2397@mail.ru, orcid.org/0000-0003-4303-0894

Nazarova O.G. - Master student, Karaganda State Technical University, e-mail: nazarova_olga_pochta@mail.ru, orcid.org/0000-0003-4166-0905

REFERENCES

- [1] Dukjoon Kim. Swelling and mechanical properties of superporous hydrogels of poly(acrylamide-co-acrylic acid)/polyethylenimine interpenetrating polymer networks / Dukjoon Kim., Kinam Park // J. Polymer. 2004. Vol. 45. Issue 1. P. 189–196.
- [2] Patent 8080595B2 USA. Process for grinding in an aqueous medium of mineral matter and binders using a reverse emulsion of a polymer acrylamide with an acrylic monomer / atrickGane, Rothrist (CH), Philipp Hunziker, Joachim Schoellkopf, Killwangen (CH).20.12.2011.
- [3] Terekhov I.V. Obtaining a copolymer of acrylonitrile and acrylic acid under conditions of living radical polymerization / I.V. Terekhov, N.V. Timoshenko, V.V. Kireyev, S.N. Filatov // Advances in Chemistry and Chemical Technology. 2010. V. 24, No. 4. P. 95.
- [4] Timoshenko N.V. Nitrile-containing imid-forming acrylic copolymers: Diss. for the degree of Cand. Chem.: specialty 02.00.06 "High molecular compounds" / N.V. Tymoshenko. Moscow, 2013. 17 p.
- [5] TakibayevaA.T., KulakovI.V., SydykovaD.M., KapbassovaA.S., RakhimberlinovaZh.B. Selecting optimal modes of knotweed raw materials pressing out and developing technology for obtaining dry extract // News of the Academy of sciences of the Republic of Kazakhstan, series chemistry and technology. 2019. № 5. P. 82-87. <https://doi.org/10.32014/2019.2518-1491.57>.
- [6] TakibayevaA.T., KulakovI.V., KapbassovaA.S., SydykovaD.M., RakhimberlinovaZh.B.Optimization of methods of quantitative determiningflavonoids in knotweed raw material// News of the Academy of sciences of the Republic of Kazakhstan, series chemistry and technology. 2019. № 5. P. 88-91. <https://doi.org/10.32014/2019.2518-1491.58>.
- [7] NurkenovO. A., Ibraev M.K., Seilkhanov T.M., Shulgau Z.T., Fazylov S.D., TakibayevaA.T. Synthesis, structure and anti-radical activity of 6-methyl-4-oxo-4H-chromen-3-acylhydrazones // News of the Academy of sciences of the Republic of Kazakhstan, series chemistry and technology. 2019. № 4. P. 25-31.<https://doi.org/10.32014/2019.2518-1491.38>.

Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации
в журнале смотреть на сайте:

www:nauka-nanrk.kz

<http://chemistry-technology.kz/index.php/en/arhiv>

ISSN 2518-1491 (Online), ISSN 2224-5286 (Print)

Редакторы: *M. С. Ахметова, Т. А. Апендиев, Аленов Д.С.*
Верстка на компьютере *A.M. Кульгинбаевой*

Подписано в печать 05.12.2019.
Формат 60x881/8. Бумага офсетная. Печать – ризограф.
5,25 п.л. Тираж 300. Заказ 6.

*Национальная академия наук РК
050010, Алматы, ул. Шевченко, 28, т. 272-13-18, 272-13-19*